

Dimensions and Tolerances
PAS 70- Site Size Test (Mean Dimensions)

BS EN771-1 requires that the dimensions of a clay masonry unit shall be declared by the manufacturer in millimetres for length, width and height, in that order. The manufacturer shall declare also which of the tolerance categories the mean values fulfill. This will take the form of T2 (generally the smallest deviation from the stated work size), T1 or Tm (manufacturers declared deviation from the stated work size, it may be wider or closer than the other categories). The tolerance is the difference between the stated work size and the average actual size.

Quick guide to mean size tolerances for standard brick dimensions.

Declared size mm	T1 Lower & upper limits	Tolerances mm	T2 Lower & upper limits	Tolerances mm	Tm
40	37-43	±3	38-42	±2	Deviation in mm declared by the manufacturer. (may be wider or closer than the other categories). Please refer to the product data sheet for Ibstock's quoted figure.
50	47-53	±3	48-52	±2	
65	62-68	±3	63-67	±2	
68	65-71	±3	66-70	±2	
73	70-76	±3	71-75	±2	
80	76-84	±4	78-82	±2	
90	86-94	±4	88-92	±2	
102	98-106	±4	99-105	±3	
190	184-196	±6	186-194	±4	
215	209-221	±6	211-219	±4	
225	219-231	±6	221-229	±4	
227	221-233	±6	223-231	±4	
290	283-297	±7	286-294	±4	

On construction sites, should a concern be raised on size and to assess whether bricks conform to the quoted tolerance, first establish which tolerance the product has been supplied to.

Sample 10 bricks by randomly choosing from a consignment and taking the selection from a minimum 6 packs where possible. Remove any superfluous material, blisters or loose particles of clay adhering to each brick.

In practice, it may not be necessary to demonstrate that all dimensions are within the tolerances stated. Place the bricks in contact with each other in a straight line upon a level, flat surface, as shown in the diagram below, ensuring that all bricks are in the same direction. DO NOT fit bricks together by alternately turning them around.


Measure the overall dimension to the nearest millimetre using a retractable steel pocket rule. Then divide the figure by 10 to give the mean value for each dimension to the nearest whole mm. Compare the figure against our stated tolerance for that product.

LENGTH Arrangement A - Faces forward (frog up if applicable).



Length measurement to nearest round mm.		Divide by 10 rounding to the nearest whole mm	
---	--	---	--


WIDTH Arrangement B - Face to back (frog up if applicable).

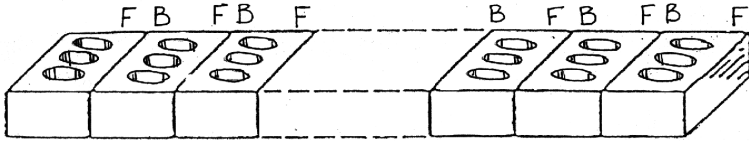

Since Ibstock supplies bricks to 102mm and not 102.5mm, measurements should be rounded to the nearest whole mm.

Width measurement to nearest round mm.		Divide by 10 rounding to the nearest whole mm	
--	--	---	--

HEIGHT Arrangement C - Faces up (frog to one common side, if applicable).

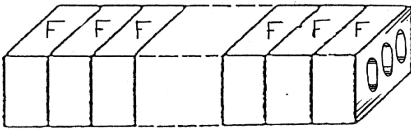

Height measurement to nearest round mm.		Divide by 10 rounding to the nearest whole mm	
---	--	---	--

The tolerance on height for 73mm products is the same as for T1 and T2 on 65mm.

For failures, borderline results or unresolved disputes, the sample of 10 bricks should be forwarded to the nearest factory for testing to BSEN772-16 using BS EN 771-1 procedures. If the Customer insists on independent verification then the sample can be sent to CERAM who will charge for performing the test. This may also cause delays on site.

RANGE VALUE

The range tolerance covers the overall difference within a sample between the largest brick and the smallest and may be called upon to resolve problems with significant size variation within a consignment.

Ten bricks must be measured individually (length, width or height), the highest and lowest figure for each declared dimension should not exceed a range as stated in the following table.

mm	40	50	65	68	73	80	90	102	140	190	215	227	290
R1	4	4	5	5	5	5	6	6	7	8	9	9	10
R2	2	2	2	3	3	3	3	3	4	4	4	5	5
Rm	A range in mm declared by the manufacturer (may be wider or closer than the other categories). Please refer to the product data sheet for quoted figure.												

For further information or advice regarding this topic please contact Ibstock’s Design & Technical Helpline on **0844 800 4576** or email technical@ibstock.co.uk

Although the instructions contained in this publication and any other information published by Ibstock Brick Ltd are believed to be accurate at the date of publication, they are strictly for guidance only and Ibstock Brick Ltd accepts no liability in relation to their use or for any losses, howsoever caused. You are responsible for taking all reasonable steps to ensure your use of the product conforms to all applicable health and safety requirements from time to time. If in doubt, please consult appropriately qualified persons. All products sold by Ibstock are sold subject to Ibstock’s Terms and Conditions of Sale, a copy of which is available on request.